



ISSN: 0976-3031

Available Online at <http://www.recentscientific.com>

CODEN: IJRSFP (USA)

International Journal of Recent Scientific Research
Vol. 8, Issue, 7, pp. 18207-18211, July, 2017

**International Journal of
Recent Scientific
Research**

DOI: 10.24327/IJRSR

Research Article

ANTIBACTERIAL AND ANTIOXIDANT PROPERTIES OF SILK FABRIC DYED WITH CICHORIUM INTYBUS ROOT EXTRACT

Krishma M. Jadav* and Ninge Gowda K.N

Department of Apparel Technology & Management, Bangalore University,
Bangalore 560001, India

DOI: <http://dx.doi.org/10.24327/ijrsr.2017.0807.0469>

ARTICLE INFO

Article History:

Received 16th April, 2017
Received in revised form 25th
May, 2017
Accepted 23rd June, 2017
Published online 28th July, 2017

Key Words:

Natural dye, *Cichorium intybus*,
Antibacterial, Antioxidant, Mordant,
Dyeing, DPPH

ABSTRACT

The present study was conducted to investigate the color strength (*K/S*), color fastness, antibacterial and antioxidant properties of silk fabric using *Cichorium intybus* root extract as a natural dye. Comparative results of color fastness (fastness to wash, rub, light and perspiration) and colorimetric properties (CIELab and *K/S* values) of dyed silk samples were studied to quantify the effect of mordants and mordanting method. Alum and Myrobalan were used as mordants. Three methods of mordanting techniques were used (pre, meta and post mordanting). The samples showed acceptable color strength and color fastness values. The antibacterial activity of the dyed samples with and without mordants was tested against common pathogens *Escherichia coli* and *Staphylococcus aureus*. The antioxidant property of the dyed fabric was analyzed by DPPH method. *Cichorium intybus* proved to be very effective in inhibiting microbial growth. The results of DPPH assay were positive for all the samples. The dyeing of silk fabric with *Cichorium intybus* root extract provided a multifunctional textile material with both antioxidant and antibacterial properties.

Copyright © Krishma M. Jadav and Ninge Gowda K.N, 2017, this is an open-access article distributed under the terms of the Creative Commons Attribution License, which permits unrestricted use, distribution and reproduction in any medium, provided the original work is properly cited.

INTRODUCTION

Value addition in clothing has changed the global textile scenario (Sathianarayanan *et al.*, 2011). Research has quite convincingly shown that apparel consumers all over the world are demanding functionality in the products (Sathianarayanan *et al.*, 2010). The wellness or health promoting aspects of textile finishes have become a delightful functional matter in the 21st century. The extracts of natural products and selected essential oils are added to textiles, which not only have healing properties but also keep the wearer fresh and vigorous (Singh *et al.*, 2011). The market for cosmetotextiles and medical textiles has greatly expanded in recent years. As textile materials have found applications in the cosmetic field, more and more commercial cosmetic textile agents are now available in the market (Cheng *et al.*, 2009). Plants are the basic source of knowledge of modern medicine. Almost all the parts of the plant, namely leaves, flowers, fruits, roots, stem and seeds are known to have various medicinal properties including antibacterial and antioxidant properties (Gousia *et al.*, 2013).

Cichorium intybus L. (Asteraceae) as an important medicinal herb has been used in folk medicine for liver disorders, gallstones and for inflammations of the urinary tract since the 17th century. The plant was used traditionally for the treatment

of diarrhea, to strengthen the prostate and other reproductive organs, for the treatment of pulmonary disease and cough, cancer, hangover, for purification of biliary tract, liver complaints, as spasmolytic, to relief of symptoms related to mild digestive disorders (such as feeling of abdominal fullness, flatulence, and slow digestion) and temporary loss of appetite. It is also reported to be used in the treatment of sore throat, hemorrhoids, tuberculosis, abdominal cramps, melancholy, deafness, rashes and as a laxative for children (Al-Snafi, 2013). Chicory is commercially used as a vegetable, fresh or cooked, while the ground and roasted roots are widely used for blending with coffee powder. It is well-known from the literature that the main active compounds of chicory are: inulin, fructooligosaccharides, caffeic acid derivatives, flavonoids and polyphenols (Kocsis, 2003). *Cichorium intybus* L. has been investigated previously to assess the content of phenolic compounds, mainly cinnamic acids and flavonoids (Innocenti, 2005). Based on the studies carried out in chicory, a worldwide report shows that the roots and leaves of this plant possess strong antibacterial and antioxidant properties (Nandagopal and Kumari, 2007; Liu *et al.*, 2013; Abbas *et al.*, 2015). However, no report exists so far on the extraction of natural dye from *Cichorium intybus* L. root and its application on silk fabric. The present study was undertaken to investigate the antibacterial

*Corresponding author: Krishma M. Jadav

Department of Apparel Technology & Management, Bangalore University, Bangalore 560001, India

and antioxidant property of the silk fabric dyed with *Cichorium intybus* root extract.

MATERIALS AND METHODS

Materials

Plain weave silk fabric, having specifications 47 g/m², 130 ends/inch and 82 picks/inch, was used for the study. The fresh chicory roots were dried under room temperature and ground to fine powder.

Extraction of color component

The extraction was carried out under an alkaline condition with MLR 1:40 at pH 10 for 90 minutes at a temperature of 90°C. The hot solution was then filtered through a Whatmann No.1 filter paper to obtain a clear filtrate. The filtrate was evaporated to produce crude which was further dried for 24 hours and ground manually using mortar and pestle to form a powder.

Selection of Mordant

Considering the eco-friendliness and cost effectiveness, the natural mordant Myrobalan (Khan *et al.*, 2005) and metallic mordant Alum (Ali *et al.*, 2009) were chosen for the dyeing process.

Dyeing and Mordanting of silk fabric

The dyeing was carried out at 90°C with the dye bath pH 5 containing 4 % of dye in crude, based on weight of fabric (owf) at MLR 1:40 in a temperature controlled open bath dyeing machine for 60 min. The fabric samples were pre, meta and post mordanted using 4% (owf) solutions of each of potassium aluminum sulphate and myrobalan separately with MLR 1:40 for 30 min at 60°C. The dyed samples were subsequently washed in 1 gpl non-ionic detergent solution at 60°C for 15 min and dried at room temperature.

Color value measurement

Color was evaluated by means of K/S and CIELAB values with illuminant D65/10° observer on Gretag Macbeth Color Eye 7000 A Spectrophotometer. Four measurements were made for each sample and the variation in percentage reflectance values over a range of 350–750 nm was recorded. The K/S values were assessed using the Kubelka-Munk equation.

$$K/S = (1-R)^2/2R$$

Where, R is the observed reflectance, K is the absorption coefficient and S is the light scattering coefficient (Swamy *et al.*, 2013; Shahid *et al.*, 2012; Swamy *et al.*, 2015).

Fastness tests

Color fastness properties of the samples were assessed using ISO standards. Color fastness to washing of dyed fabric was determined as per ISO 105-C06 test method. Color fastness to crocking/ rubbing was assessed as per ISO105-X12 test method. Color fastness to light was determined as per AATCC 16.3:2012 method and Color fastness to perspiration was assessed as per ISO 105-E04 1994 method (Shahid *et al.*, 2012; Swamy *et al.*, 2015; Ali *et al.*, 2009; Purwar *et al.*, 2016).

Determination of Antibacterial activity of dyed fabrics

The antibacterial activity was assessed by qualitative testing of fabric using Antibacterial Activity Assessment of Textile Materials: Parallel Streak Method [AATCC Test Method 147-2004 (Sathianarayanan *et al.*, 2011)]. *Escherichia coli* (*E.coli*), a gram-negative bacterium and *Staphylococcus aureus* (*S. aureus*), a pathogenic gram-positive bacterium were selected for the study (El-Molla *et al.*, 2011; Mahish *et al.*, 2012) as they are recommended in most test methods (Gao and Cranston, 2008; Shaki *et al.*, 2015). Briefly, the test strains were inoculated in sterile nutrient broth and were allowed to grow for 18 h at 37° C. Sterile nutrient agar plates were prepared for each test strain and one loop (4 mm in size) full of overnight grown bacterial culture was inoculated on the surface of nutrient agar plate by making five parallel inoculum streaks in such a way that it should cover the central area of the Petri dish without refilling the loop of the same inoculum. Then *Cichorium intybus* treated fabrics were placed transversely across five inoculum streaks made earlier on the plate. The fabrics were pressed gently using sterile spatula (flame sterilization) to ensure that *Cichorium intybus* treated fabrics have an intimate contact with nutrient agar surface. Simultaneously, the plate containing untreated fabrics was also maintained as control and the plates were incubated for 24 h at 37° C. At the end of the incubation, a clear area showing no growth along the sides of *Cichorium intybus* treated fabrics indicates the antibacterial activity and then ZOI was calculated. The average width of inhibition zone on either side of the *Cichorium intybus* treated fabrics along the streak was calculated using the following equation,

$$W = (T-D)/2$$

Where, W = Width of clear zone of inhibition (mm); T = Total diameter of test specimen and the zone of clearance (mm); D = Diameter of the test specimen (mm).

Determination of Antioxidant Activity (DPPH assay)

Radical scavenging activity of the dyed silk fabric was determined by measuring the decrease in absorbance of 2,2-Diphenyl-1-picrylhydrazyl radical (DPPH•) at 517 nm (Khadabadi *et al.*, 2013). The DPPH assay is a widely used method to evaluate the ability of antioxidants (Sahgal *et al.*, 2009) to scavenge free radicals which are known to be a major factor in biological damages caused by oxidative stress. This assay is known to give reliable information concerning the antioxidant ability of the tested compounds (Grace-Lynn *et al.*, 2012; Huang *et al.*, 2005; Parthasarathy *et al.*, 2009). This method is based on the ability of DPPH radical to react with hydrogen donor species such as phenolics and flavonoids present in the extracted material. Upon receiving a proton from the donor species it loses its color and becomes yellow. As the concentration of phenolic compounds increases, their DPPH radical scavenging activity also increases (Porto *et al.*, 2000). The fabric samples were kept immersed in DMSO for a time period of 1 hour at MLR 1:10. The DMSO solution was then filtered and collected from each fabric sample. The solution was evaporated to dryness and the crude collected was weighed and dissolved in DMSO (10mg/ml). This was considered as pure sample extract for testing the antioxidant property. 0.3mM solution of DPPH was prepared in 100% methanol. To 1ml of

this solution, three different concentrations 100µl, 300µl and 500µl of sample extract and standard solution (Ascorbic acid) were added separately. The final volume was made up to 4ml by adding 100% methanol to each sample mixture and also for standard solution (Ascorbic acid). The same reaction mixture without the extract sample but with equivalent amount of standard phosphate buffer was taken as control. All the sample mixtures and control were shaken thoroughly, and kept in dark at room temperature for 30 mins. The absorbance of the reaction mixtures were measured at 517 nm. The radical scavenging activities were expressed as a percentage of inhibition and calculated according to the following equation.

$$\% \text{ DPPH inhibition} = [(AC-AS)/AC] \times 100$$

Where AC = absorbance of control and AS = absorbance of test sample (Rao *et al.*, 2011; Aqil *et al.*, 2006).

RESULTS AND DISCUSSION

Color Characteristics

K/S values of the samples indicate that the concentration and kind of mordant and mordanting methods significantly affect the lightness, shade and color yield. Results with respect to color depth (K/S values) of silk fabric dyed with root extract of *Cichorium intybus* obtained with and without the use of mordants are given in Table 1. From the results, it is clear that both mordants and mordanting methods have an influence on the color strength values. All the mordanted samples show higher dye uptake than that of the unmordanted (control) sample. Maximum color strength of K/S (15.14) was obtained with sample pre-mordanted with myrobalan, whereas the unmordanted (control) sample showed the lowest K/S value of 7.36. The process of dyeing with different mordants gives a shade change from light to golden brown. Myrobalan mordanted samples showed higher color strength valued compared to alum mordanted samples. Varied hues of color are obtained from pre, meta and post mordanting with Alum and Myrobalan.

Table 1 K/S and color co-ordinates of Silk fabric dyed with *Cichorium intybus* root extract

Sample	Mordanting Method	K/S	L*	a*	b*	c	H
Control	-	7.36	62.996	10.865	38.101	39.62	74.083
Alum Mordanted	Pre	10.64	56.653	11.922	37.845	39.678	72.515
	Meta	8.28	62.744	10.405	38.754	40.126	74.971
	Post	10.38	55.066	11.644	35.519	37.379	71.85
Myrobalan Mordanted	Pre	15.14	54.753	8.087	33.672	34.629	76.496
	Meta	13.72	58.339	7.343	34.283	35.061	77.911
	Post	14.64	56.181	10.121	35.677	37.085	74.163

Fastness properties

The evaluation of color fastness to washing, rubbing, light and perspiration using Alum: pre, simultaneous and post mordanting method and Myrobalan: pre, simultaneous and post mordanting method are presented in Table 2. All the alum mordanted samples including control sample which were subjected to washing fastness showed fair color fastness to color change and poor to fair color fastness to staining. The myrobalan mordanted samples have shown good to fairly good color fastness to color change and color staining. The dry and wet rubbing fastness grades for control and alum mordanted samples were 2-3 (poor to fair) and grades for myrobalan mordanted samples were in between 4 and 3-4. The light

fastness of control and alum mordanted samples was very poor to poor, whereas the Myrobalan mordanted samples showed fairly good to fair fastness. In case of perspiration fastness, the grades for color change in both acidic and alkaline media for control and all alum mordanted samples were fair to fairly good (3 to 3-4) and grades for color staining were 2-3 (poor to fair). All the Myrobalan mordanted samples showed better color fastness properties compared to control and alum mordanted samples.

Table 2 Fastness properties of silk fabric dyed with *Cichorium intybus* root extract

Sample	Mordanting Method	Washing fastness grades		Rubbing fastness grades		Light fastness grades	Perspiration fastness grades			
		CC	CS	Dry	Wet	CC	Acidic		Alkaline	
							CC	CS		
Control		3	2-3	3	3	1-2	3	2-3	3	2
Alum Mordanted	Pre	3	2-3	2-3	2-3	1-2	3-4	2-3	3-4	2-3
	Meta	3	2-3	2-3	2-3	1	3	2-3	3	2-3
	Post	3	3	2-3	2-3	1	3	2-3	3	2-3
Myrobalan Mordanted	Pre	4	4	3-4	3	3	4	3-4	4	3-4
	Meta	4	3-4	3-4	3-4	3-4	4	3-4	4	3
	Post	4	4	4	3-4	3	4	4	4	3

Antibacterial properties

The antibacterial property is qualitatively evaluated by AATCC Test Method 147-2004 against gram-negative (*E.coli*) and gram-positive (*S. aureus*) bacterium. The results (Table 3.) show that all the treated fabrics, including unmordanted sample have very good antibacterial property to gram-negative and gram-positive bacterium, *E. coli* and *S. aureus*. In all the cases, there is a good zone of inhibition ranging from 1.4 mm to 3.7 mm against *E.coli* and 1.2 mm to 2.65 mm against *S. aureus*. The mordanted samples showed increased zone of inhibition compared to unmordanted sample (dyed without mordant). From the results shown in Table 3 it is clear that all the myrobalan mordanted samples showed higher zone of inhibition compared to alum mordanted samples.

Table 3 Antimicrobial activity of Silk fabric dyed with *Cichorium intybus* root extract

Sample	Mordanting Method	Zone of inhibition, mm	
		<i>E. coli</i>	<i>S. aureus</i>
Positive Control	-	4.1	4.9
Negative Control	-	Nil	Nil
Unmordanted Mordanted		1.4	1.2
	Alum	2.7	2.2
	Meta-mord	2.9	1.7
	Post-mord	2.7	1.6
	Pre-mord	3.7	2.65
	Myrobalan	3.4	2.4
	Post-mord	3.7	2.7

Antioxidant properties

DPPH radical scavenging activity of Ascorbic acid, control and pre, post and simultaneous mordanted samples with alum and myrobalan are shown in Fig 1. and Fig 2. The activity was increased by increasing the concentration of the sample extract (100µL, 300µL and 500µL). DPPH antioxidant assay is based on the ability of 2,2-Diphenyl-1-picrylhydrazyl radical (DPPH), a stable free radical, to decolorize in the presence of antioxidants. The DPPH radical contains an odd electron, which is responsible for the absorbance at 517 nm and also for

a visible deep purple color. When DPPH accepts an electron donated by an antioxidant compound, the DPPH is decolorized, which can be quantitatively measured from the changes in absorbance. Ascorbic acid was used as Standard. All the samples dyed with *Cichorium intybus* root extract showed excellent increased % inhibition with the increase in concentration of extract proving it to be a potential Antioxidant. The control sample dyed without mordant showed % inhibition of 88.14% at 500 µl concentration. Among all the mordant-dyed samples, silk pre-mordanted with myrobalan showed the highest % inhibition (92.35%) followed by myrobalan post-mordanted with % inhibition of 92.06% and myrobalan meta-mordanted with % inhibition 91.04%. The samples mordanted with myrobalan showed higher antioxidant activity compared to alum mordanted samples. However, all the samples including the control sample (dyed without mordant) showed positive results for DPPH assay.

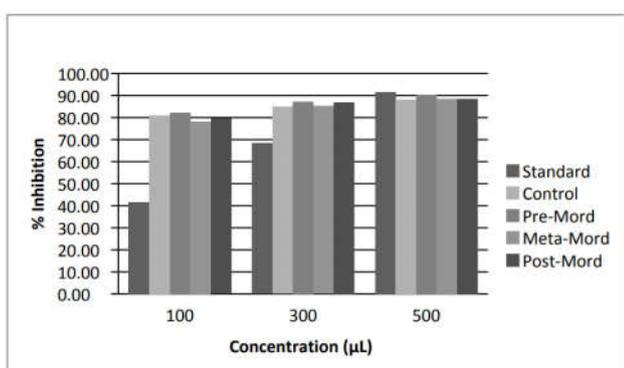


Fig 1 DPPH assay of Alum mordanted silk samples dyed with *Cichorium intybus* root extract

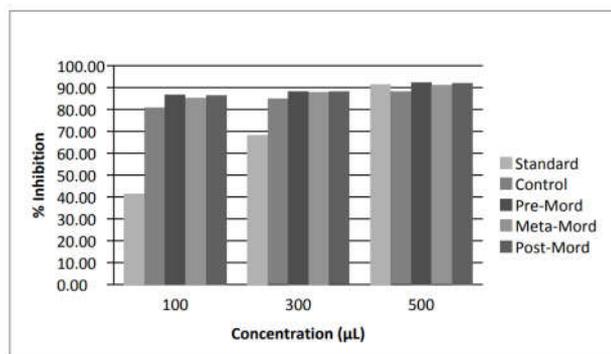


Fig 2 DPPH assay of Myrobalan mordanted silk samples dyed with *Cichorium intybus* root extract

CONCLUSION

Silk fabric was treated with natural dye extracted from *Cichorium intybus* roots in order to produce a multifunctional textile material with antibacterial and antioxidant properties. From the study it is revealed that mordants and mordanting methods have a synergistic effect on color strength, color fastness, antibacterial and antioxidant properties. Mordant treatment not only improved the color strength and color fastness properties of the sample but also added to its antibacterial and antioxidant properties. The dyed samples showed good inhibition to microbial growth. The antioxidant activity of the samples was excellent and found to be increased with the increase in concentration of the dye extract. The

treatment of silk fabric with *Cichorium intybus* root extract provided a textile material with both antibacterial and antioxidant properties and acceptable color strength and color fastness properties.

References

- Abbas ZK, Saggua S, Sakeranb MI, Zidand N, Rehmana H and Ansari AA: Phytochemical, antioxidant and mineral composition of hydroalcoholic extract of chicory (*Cichorium intybus* L.) leaves. *Saudi Journal of Biological Sciences* 2015; 22(3): 322-326
- Ali S, Hussain T and Nawaz R: Optimization of alkaline extraction of natural dye from Henna leaves and its dyeing on cotton by exhaust method. *Journal of Cleaner Production* 2009; 17: 61-66
- Ali S, Hussain T and Nawaz R: Optimization of alkaline extraction of natural dye from Henna leaves and its dyeing on cotton by exhaust method. *Journal of Cleaner Production* 2009; 17: 61-66
- Al-Snafi AE: Medical importance of *Cichorium intybus* - A review. *IOSR Journal of Pharmacy* 2013; 6(3): 41-56
- Aqil F, Ahmad I and Mehmood Z: Antioxidant and Free Radical Scavenging Properties of Twelve Traditionally Used Indian Medicinal Plants. *Turkish Journal of Biology* 2006; 30: 177-183
- Cheng SY, Yuen CWM, Kan CW and Li SY: A Comprehensive Study of Silicone-based Cosmetic Textile Agent. *Fibers and Polymers* 2009; 10(1): 132-140
- El-Molla MM, El-Khatib EM, El-Gammal MS and Abdel-Fattah SH: Nanotechnology to improve coloration and antimicrobial properties of silk fabrics. *Indian Journal of Fibre & Textile Research* 2011; 36: 266-271
- Gousia SK, Kumar KA, Kumar TV and Latha JNL: Biological Activities and Medicinal Properties of *Couroupita guianensis*. *International Journal of Pharmacy and Pharmaceutical Science Research* 2013; 3(4): 140-143
- Gao Y and Cranston R: Recent Advances in Antimicrobial Treatments of Textiles. *Textile Research Journal* 2008; 78(1): 60-72
- Grace-Lynn C, Darah I, Chen Y, Latha L Y, Jothy SL and Sasidharan S: In Vitro Antioxidant Activity Potential of Lantadene A, a Pentacyclic Triterpenoid of Lantana Plants. *Molecules* 2012; 17: 11185-11198
- Huang D, Ou B and Prior RL: The chemistry behind antioxidant capacity assays. *Journal of Agricultural and Food Chemistry* 2005; 53: 1841-1856
- Innocenti M, Gallori S, Giaccherini C, Ieri F, Vincieri FF and Mulinacci N: Evaluation of the Phenolic Content in the Aerial Parts of Different Varieties of *Cichorium intybus* L. *Journal of Agricultural and Food Chemistry* 2005; 53: 6497-6502
- Khan MA, Khan M, Srivastava PK and Mohammad F: Extraction of natural dyes from myrobalan, gallnut and pomegranate, and their application on wool. *Colorage* 2005; 52: 53-60
- Khadabadi SS, Deore SL and Baviskar BA: Quantitative Chemical Estimation. Experimental Phytopharmacognosy. Nirali Prakashan Pub, India, Second Edition 2013
- Kocsis I, Hagymasi K, Kery A, Szoke E and Blazovics A: Effects of chicory on pancreas status of rats in

- experimental dyslipidemia. *Acta Biologica Szegediensis* 2003; 47(1-4): 143-146
- Liu H, Wang Q, Liu Y, Chen G and Cui J: Antimicrobial and Antioxidant Activities of *Cichorium Intybus* Root Extract Using Orthogonal Matrix Design. *Journal of Food Sciences* 2013; 78(2): 258-263
- Mahish SS, Patra AK and Thakur R: Functional properties of bamboo/polyester blended knitted apparel fabrics. *Indian Journal of Fibre & Textile Research* 2012; 37: 231-237
- Nandagopal S and Kumari BDR: Phytochemical and Antibacterial Studies of Chicory (*Cichorium intybus L.*) - A Multipurpose Medicinal Plant. *Advances in Biological Research* 2007; 1(1-2): 17-21
- Purwar R, Sahoo P, Jain M, Bothra U, Yadav P, Jigyashu J and Mohan C: Dope dyeing of polyacrylonitrile filaments with Ratanjot. *Indian Journal of Fibre & Textile Research* 2016; 41(1): 84-88
- Parthasarathy S, Azizi JB, Ramanathan S, Ismail S, Sasidharan S, Said MIM and Mansor SM: Evaluation of Antioxidant and Antibacterial Activities of Aqueous, Methanolic and Alkaloid Extracts from *Mitragyna Speciosa* (Rubiaceae Family) Leaves. *Molecules* 2009; 14: 3964-3974
- Porto CD, Calligaris S, Cellotti E and Nicoli MC: Antiradical properties of commercial cognacs assessed by the DPPH• test. *Journal of Agricultural and Food Chemistry* 2000; 48: 4241-4245
- Rao KS, Munjuluri PR and Keshar NK: In vitro Antioxidant Activity and Total Phenolic Content of *Mimusops elengi* Bark. *Indian Journal of Pharmaceutical Education and Research* 2011; 45: 317-323
- Sathianarayanan MP, Chaudhari BM and Bhat NV: Development of durable antibacterial agent from banajwain seed (*Thymus serpyllum*) for cotton fabric. *Indian Journal of Fibre & Textile Research* 2011; 36: 234-241
- Sathianarayanan MP, Bhat NV, Kokate SS and Walunj VE: Antibacterial finish for cotton fabric from herbal products. *Indian Journal of Fibre & Textile Research* 2010; 35: 50-58
- Sathianarayanan, MP, Chaudhari BM and Bhat NV: Development of durable antibacterial agent from banajwain seed (*Thymus serpyllum*) for cotton fabric. *Indian Journal of Fibre & Textile Research* 2011; 36: 234-241
- Sahgal G, Ramanathan S, Sasidharan S, Mordi MN, Ismail S and Mansor SM: In Vitro Antioxidant and Xanthine Oxidase Inhibitory Activities of Methanolic *Swietenia mahagoni* Seed Extracts. *Molecules* 2009; 14: 4476-4485
- Shaki H, Gharanjig K and Khosravi A: Spectral, dyeing and antimicrobial properties of some monoazo naphthalimide dyes on polyamide. *Indian Journal of Fibre & Textile Research* 2015; 40: 425-430.
- Shahid M, Ahmad A, Yusuf M, Khan MI, Khan SA, Manzoor N and Mohammad F: Dyeing, fastness and antimicrobial properties of woolen yarns dyed with gallnut (*Quercus infectoria* Oliv.) extract. *Dyes and Pigments* 2012; 95: 53-61
- Singh MK, Varun VK and Behera BK: Cosmetotextiles: State of Art. *Fibres & Textiles in Eastern Europe* 2011; 19: 27-33
- Swamy VN, Gowda KNN and Sudhakar R: Natural Dye From the Bark of *Casuarina Equisetifolia* for Silk. *International Journal of Pharma and Bio Sciences* 2013; 4(3)(B): 94-104
- Swamy VN, Gowda KNN and Sudhakar R: Dyeing of Silk using *Madhuca longifolia* as natural dye source. *Indian Journal of Fibre & Textile Research* 2015; 40(4): 419-424

How to cite this article:

Krishma M. Jadav and Ninge Gowda K.N., Antibacterial and Antioxidant Properties of Silk Fabric Dyed with *Cichorium Intybus* Root Extract. *Int J Recent Sci Res.* 8(7), pp. 18207-18211. DOI: <http://dx.doi.org/10.24327/ijrsr.2017.0807.0469>
